

# Propane reacts with O<sub>2</sub> and H<sub>2</sub> on gold supported TS-1 to form oxygenates with high selectivity†

J. J. Bravo-Suárez,<sup>a</sup> K. K. Bando,<sup>a</sup> T. Akita,<sup>b</sup> T. Fujitani,<sup>a</sup> T. J. Fuhrer<sup>c</sup> and S. T. Oyama<sup>\*ad</sup>

Received (in Berkeley, CA, USA) 15th January 2008, Accepted 6th May 2008

First published as an Advance Article on the web 13th June 2008

DOI: 10.1039/b800620b

**Gold nanoparticles supported on a microporous titanosilicate (TS-1) were found to be highly selective (95%) towards the formation of acetone and isopropanol from propane, O<sub>2</sub>, and H<sub>2</sub> at moderate temperatures (443 K).**

Propane partial oxidation to high value products has been a long sought goal. Examples of such products include acrylic acid and acrylonitrile,<sup>1</sup> as well as acetone and isopropanol. Acetone, for example, is mainly produced as a co-product in the synthesis of phenol by the cumene process, with a world production of 5.2 million metric tons in 2004.<sup>2</sup> Future planned processes for directly obtaining phenol from benzene will necessitate alternative routes for acetone.<sup>3</sup> Isopropanol is produced by hydration of propylene using acid catalysts, with a total world capacity of 1.9 million metric tons in 1996.<sup>4</sup> This process requires high pressures and suffers from corrosion problems. Alternative acetone and isopropanol production methods from propane have been studied. In these methods, propane reacts with O<sub>2</sub> or hydroperoxides at mild temperatures and high pressures using biomimetic complexes (*e.g.*, Fe, Co, or Cu porphyrins, phthalocyanines, and oxometalates)<sup>5–9</sup> or Ti, V, or Fe containing catalysts.<sup>6–9</sup> An ideal process from low-cost abundant propane should be continuous, produce oxygenates with high selectivity, use O<sub>2</sub> as the oxidant at moderate conditions, and use a recyclable catalyst. None of the above methods fulfils all these requirements.

Here it is shown that propane can be converted continuously to acetone and, in lesser amounts, isopropanol with high selectivity (95%) under mild conditions (443 K and 0.3 MPa) using a mixture of O<sub>2</sub> and H<sub>2</sub> as the oxidizing agent and Au–Ba/TS-1 as the catalyst. Evidence is presented for the presence of intermediates during the reaction, including adsorbed oxygen on Au and hydroperoxide species on Ti.

The Au–Ba/TS-1 catalysts were prepared by the deposition–precipitation (DP) method<sup>10</sup> using Na<sub>2</sub>CO<sub>3</sub> as the neutralizing agent, a pH of 9, and TS-1 as the support (see ESI† for details†). Ba was added to improve the Au capture by the support.<sup>10</sup> The Au loadings were about 0.1 wt% and Au particle sizes about 4.0 nm (see ESI†). Propane oxidation

was carried out at 443 K and 0.3 MPa, with O<sub>2</sub> and H<sub>2</sub>. The catalysts (Ti : Si = 2 : 100, 3 : 100, and 10 : 100) formed mostly acetone with some isopropanol in combined selectivities of over 85% and propane conversions of 2.1–6.5% (Table 1). In particular, the Au–Ba/TS-1 catalyst with an intermediate Ti : Si = 3 : 100 ratio presented the most remarkable catalytic results with an oxygenate selectivity of 95% at a propane conversion 6.5%, which corresponded to acetone and isopropanol space-time yields (STY) of 33 and 2 g kg<sub>cat</sub><sup>–1</sup> h<sup>–1</sup>, respectively. The resulting acetone TOF was 0.079 s<sup>–1</sup> based on exposed Au. The Au loadings in the samples were similar, with a slightly higher value for the catalyst with Ti : Si = 3 : 100. The difference in reactivities is likely due to an optimum Ti : Si ratio that allows the formation of a maximum number of effective Ti sites in the zeolite framework.<sup>11</sup> Here, the best Ti : Si ratio of 3 : 100 corresponds well with previously reported maximum contents of Ti in TS-1 zeolite framework positions.<sup>12</sup>

Catalytic oxidation with O<sub>2</sub> and H<sub>2</sub> on Au/TiO<sub>2</sub>–SiO<sub>2</sub> likely occurs by *in situ* formation of H<sub>2</sub>O<sub>2</sub> on Au. The H<sub>2</sub>O<sub>2</sub> then transfers to Ti tetrahedral sites to form Ti–OOH species active for selective oxidations, such as propylene epoxidation.<sup>13,14</sup> In the case of propane, a similar mechanism may take place, and the involvement of isopropoxy intermediate species could explain the formation of acetone and isopropanol.

*In situ* UV-Vis spectra of Au–Ba/TS-1 (Ti : Si = 3 : 100) under propane oxidation conditions show evidence for the formation of the Ti–OOH species. Changes occur in several regions (Fig. 1 and ESI†): (1) a band at about 540 nm due to a plasmon resonance (PR) of Au nanoparticles<sup>15</sup> (Au is mostly metallic as evidenced by the absence in the Au L<sub>3</sub>-edge XANES of a near-edge resonance around 11 920 eV due to oxidized Au, see ESI†); (2) band growth at 320–410 nm and 210–240 nm due to Ti–hydroperoxo species;<sup>12,16</sup> and (3) a band decrease at 250–300 nm due to tripodal Ti sites, Ti(Os)<sub>3</sub>–OH·(H<sub>2</sub>O)<sub>2</sub>.<sup>12</sup> These assignments are supported by density functional theory (DFT) calculations (see ESI†). The Au PR position as a function of reaction time (Fig. 1a) shows an initial increase (red shift) during the first 0.1 h, followed by a decrease (blue shift), reaching a constant value (539.4 nm) after 3 h. The initial red shift is related to O<sub>2</sub> adsorption on Au,<sup>17</sup> while the subsequent blue shift is explained by reaction of O<sub>2</sub>, most likely with H<sub>2</sub> to form H<sub>2</sub>O<sub>2</sub>. The steady-state Au PR position (539.4 nm) was higher than that observed under H<sub>2</sub> flow (534.1 nm), confirming the presence of adsorbed O<sub>2</sub> on Au during reaction. Although an adsorbed superoxide O<sub>2</sub><sup>–</sup> species has been observed by electron paramagnetic resonance spectroscopy,<sup>16</sup> to the best of our knowledge, this is the first *in situ* experimental evidence of adsorbed oxygen on Au

<sup>a</sup> National Institute of Advanced Industrial Science and Technology (AIST), 16-1 Onogawa, Tsukuba, 305-8569, Japan

<sup>b</sup> AIST, Midorigaoka 1-8-31, Ikeda 563-8577 Osaka, Japan

<sup>c</sup> Chemistry and Physics, Radford University, Radford, VA 24142, USA

<sup>d</sup> Chemical Engineering, Virginia Tech, Blacksburg, VA 24061, USA.  
E-mail: oyama@vt.edu; Fax: +1 540 231 5022;  
Tel: +1 540 231 5309

† Electronic supplementary information (ESI) available: Experimental section, TEM, Au L<sub>3</sub> edge XANES and UV-Vis data. See DOI: 10.1039/b800620b


**Table 1** Catalytic reactivity of Au–Ba/Ts-1 catalysts for propane partial oxidation

Nominal Ti : Si ratio	[Au] (wt%) <sup>a</sup>	D <sub>p</sub> /nm <sup>b</sup>	Conversion (%)		Selectivity (%)		H <sub>2</sub> efficiency (%) <sup>c</sup>			Main product <sup>d</sup>	
			C <sub>3</sub> H <sub>8</sub>	H <sub>2</sub>	Acetone	2-Propanol	C <sub>3</sub> H <sub>6</sub>	CO <sub>2</sub>	STY/g kg <sub>cat</sub> <sup>-1</sup> h <sup>-1</sup>	TOF/s <sup>-1</sup>	
2 : 100	0.09	4.4	2.1	7	92	2	0	6	10	10	0.032
3 : 100	0.11	4.0	6.5	10	90	5	0	5	17	33	0.079
10 : 100	0.07 <sup>e</sup>	4.2	2.5	5	83	2	0	15	42	12	0.047
10 : 100 <sup>f</sup>	0.02	—	0.4	5	89	0	0	11	16	2	0.031
∞ <sup>g</sup>	1.2	2.7	1.4	15	4	0	69	27	16	120	0.029


<sup>a</sup> Au content by ICP-AES. <sup>b</sup> Au average size by TEM. <sup>c</sup> H<sub>2</sub> selectivity to C<sub>3</sub>-products. <sup>d</sup> (STY: space-time yield; TOF: turnover frequency) TOF based on exposed Au. Au dispersion is calculated from particle size, assuming Au fcc packing and spherical particles. <sup>e</sup> Estimated from Au L<sub>3</sub>-XAFS edge-jump intensity. <sup>f</sup> Without Ba. <sup>g</sup> Au/TiO<sub>2</sub> (P25) with C<sub>3</sub>H<sub>8</sub> : H<sub>2</sub> : O<sub>2</sub> : Ar = 2 : 1 : 1 : 6, 443 K, 0.1 MPa, SV (space velocity) = 36000 cm<sup>3</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>. Reaction conditions: C<sub>3</sub>H<sub>8</sub> : H<sub>2</sub> : O<sub>2</sub> : Ar = 0.5 : 3 : 1 : 5.5, 443 K, 0.3 MPa, SV ~ 4500 cm<sup>3</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>. Reactivity after 0.5 h.

supported on a titanosilicate. Propane conversion and selectivities on Au/Ts-1 appeared to track with spectroscopic changes (see ESI†); however, to prove that the observed species are true intermediates would require the use of transient spectroscopic techniques.<sup>14,18</sup>

*In situ* UV-Vis spectra (Fig. 1b) initially show hydrated hydroxyl species Ti(OSi)<sub>3</sub>-OH·(H<sub>2</sub>O)<sub>2</sub> that react (decrease in 270 nm band) with H<sub>2</sub>O<sub>2</sub> to form hydroperoxide species. The latter are dehydrated Ti(OOH) (225 nm band) and hydrated Ti-OOH (360 nm band) species. DFT calculations provide the assignments (see ESI†). Overall, the *in situ* PR and UV-Vis spectroscopy results are consistent with the adsorption of oxygen on the gold nanoparticles followed by activation with H<sub>2</sub> to produce H<sub>2</sub>O<sub>2</sub>, which transfers to a Ti center to form hydroperoxide species (Scheme 1). In the scheme Au represents a gold cluster, not an isolated gold atom.

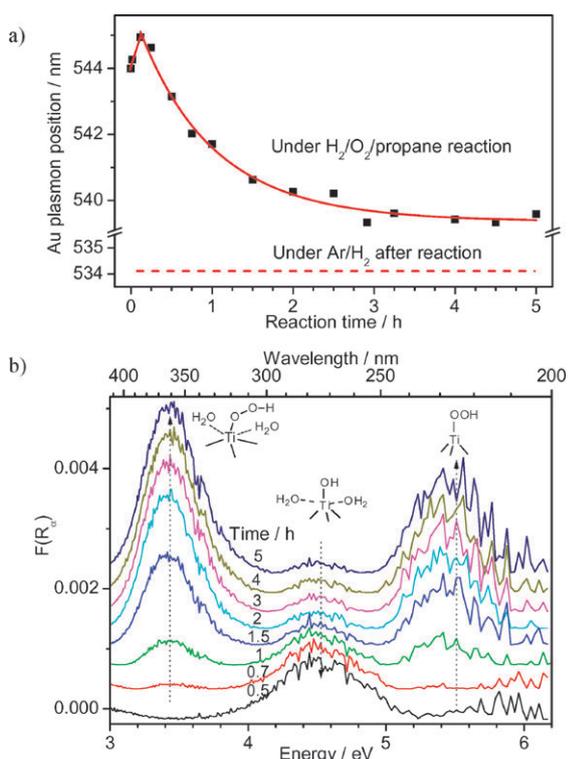

**Fig. 1** *In situ* UV-Vis spectra for Au–Ba/Ts-1 (Ti : Si = 3 : 100) under reaction conditions: (a) Au plasmon resonance position, and (b) difference spectra with catalyst before reaction under Ar.

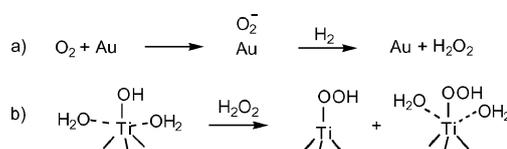


**Scheme 1** Sequence of steps in oxygen activation: (a) H<sub>2</sub>O<sub>2</sub> formation on gold; (b) hydroperoxide formation on Ti centers.


The main products of reaction on the gold catalysts were acetone (TS-1 support) and propylene (TiO<sub>2</sub> support). It has been proposed that propane activation on TS-1 yields an isopropoxy intermediate,<sup>19</sup> and this is likely the case for these catalysts (Scheme 2a). A 2° proton on propane (most acidic) undergoes attack by the terminal OH on the hydroperoxide, and the electrons from the C–H bond transfer to the proximal peroxide oxygen (most electropositive). The propoxy species could produce acetone (Scheme 2b) or propylene (Scheme 2c), as is observed for isopropanol on basic oxides.

The different selectivities of the TS-1 and TiO<sub>2</sub> supports could arise from differences in their acid–base properties.<sup>20</sup> Temperature-programmed desorption (TPD) traces of CO<sub>2</sub> and NH<sub>3</sub> from Au–Ba/Ts-1 (Ti : Si = 3 : 100) and Au/TiO<sub>2</sub> catalysts, and their corresponding supports clearly show marked differences (Fig. 2). The Au–Ba/Ts-1 sample mainly has small amounts of weak acid and base sites, while the Au/TiO<sub>2</sub> catalyst also has stronger basic and acidic sites and in larger concentrations.

Under the oxidizing conditions of the present study acetone formation is expected to proceed by reaction of the

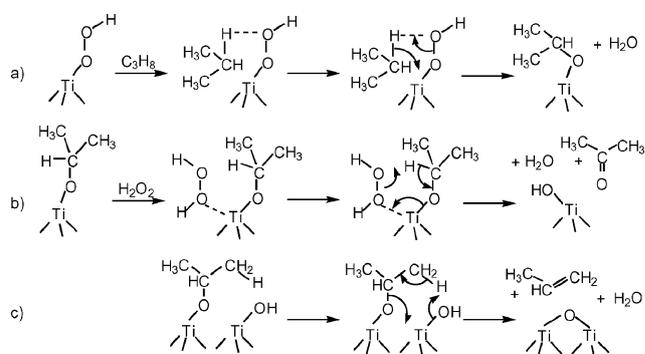

**Scheme 2** Possible sequence of steps during propane selective oxidation on gold supported Ti-containing catalysts: (a) formation of the isopropoxy intermediate; (b) oxidation of the isopropoxy species to acetone; (c) dehydration of the isopropoxy species to propylene.

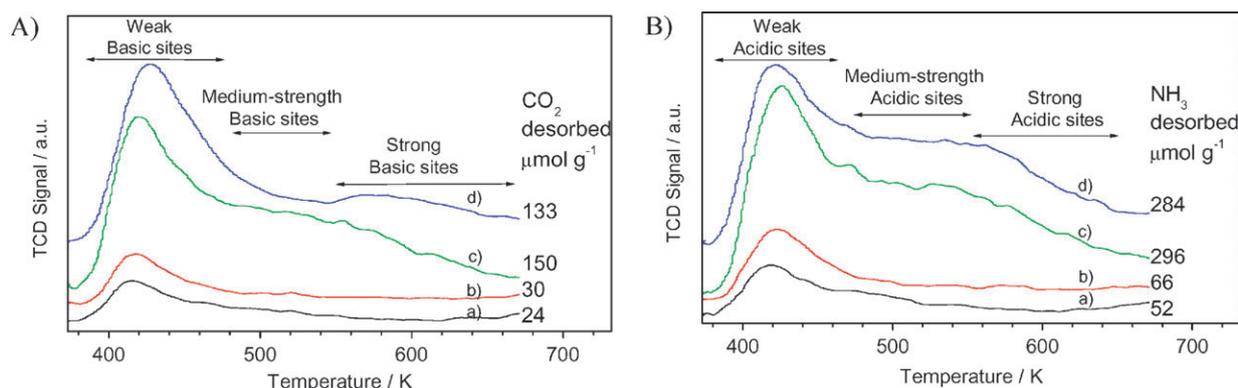

**Fig. 2** (A) CO<sub>2</sub> and (B) NH<sub>3</sub> temperature-programmed desorption traces for different gold supported catalysts and supports. (a) TS-1 (Ti : Si = 3 : 100); (b) Au-Ba/TS-1 (Ti : Si = 3 : 100); (c) TiO<sub>2</sub> (P25); and (d) Au/TiO<sub>2</sub>.

isopropoxide intermediate with H<sub>2</sub>O<sub>2</sub> (Scheme 2b). On the other hand, propylene formation likely occurs by dehydration of isopropoxy species. In analogy with isopropanol reactions on metal oxides, this would be expected to occur on strong-weak or weak-strong acid-base pair sites present on the TiO<sub>2</sub> support, possibly *via* concerted E<sub>2</sub> or E<sub>1cB</sub> mechanisms, respectively.<sup>21</sup> The E<sub>2</sub> dinuclear elimination mechanism involves transfer of a proton on the adsorbed propoxy species to a surface OH group, with simultaneous loss of the surface oxygen link (Scheme 2c).<sup>22,23</sup> The E<sub>1cB</sub> mononuclear elimination mechanism is similar, but occurs in two steps, with the proton abstracted first.<sup>22,23</sup> This is unlikely in the present case because the Ti group is not a sufficiently strong base. The Ba component is probably not involved in the reaction, as unpromoted Au/TS-1 catalysts show similar conversion and selectivity. As mentioned earlier, its main role is to increase the Au loading (Table 1).<sup>10</sup>

Propane oxidation has been previously reported in a H<sub>2</sub>-O<sub>2</sub> cell system at 298 K. Acetone (39%) and acetaldehyde (13%) were produced at a STY of only 6 g kg<sub>cathode</sub><sup>-1</sup> h<sup>-1</sup>.<sup>24</sup> More recently, propane oxidation mediated by a Fe<sup>2+</sup>-H<sub>2</sub>O<sub>2</sub> Fenton system was carried out in a three-phase catalytic hollow fiber membrane reactor. Total oxygenate selectivity (acetone, isopropanol, *n*-propanol, and propanal) was 96%, but the STY reached only 5 g kg<sub>membrane</sub><sup>-1</sup> h<sup>-1</sup>.<sup>8</sup> In the present study propane is oxidized with O<sub>2</sub> and H<sub>2</sub> to acetone and isopropanol with a high selectivity of 95% and a STY of 35 g kg<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>, which is much higher than previously reported yields and is similar to that obtained in a batch system using costly H<sub>2</sub>O<sub>2</sub> and TS-1 with a selectivity to oxygenates (acetone and isopropanol) close to 100% and a STY of 79 g kg<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>.<sup>9</sup>

In conclusion, it has been demonstrated that Au supported on TS-1 are active catalysts for propane oxidation with O<sub>2</sub> and H<sub>2</sub>, and highly selective towards the formation of acetone and isopropanol, with space-time yields (STY) comparable to those obtained with liquid H<sub>2</sub>O<sub>2</sub> in a batch reactor.<sup>9</sup> These results are encouraging as further improvements in the catalytic and reactor system will likely yield much higher STYs. *In situ* spectroscopic data and catalyst characterization reveal the presence of possible reaction intermediates (O<sub>2</sub> adsorbed on metallic Au, Ti-OOH, and isopropoxy species) and contribute

to a better understanding of gas-phase catalyzed oxidations on gold supported catalysts.

Support was provided by the Ministry of Economy, Trade and Industry, the National Science Foundation, the Japan Society for the Promotion of Science, and KEK-PF.

## Notes and references

- J. F. Brazdil, *Top. Catal.*, 2006, **38**, 289.
- Z.-C. He, *Xiandai Huagong*, 2005, **25**(11), 61.
- P. P. Notté, *Top. Catal.*, 2000, **13**, 387.
- A. J. Papa, Propanols, in *Ullmann's Encyclopedia of Industrial Chemistry [online]*, Wiley Interscience, Weinheim, Germany, posted: June 15, 2000.
- H. Sun, F. Blatter and H. Frei, *Catal. Lett.*, 1997, **44**, 247.
- N. Mizuno, *Catal. Surv. Jpn.*, 2000, **41**, 49.
- R. Raja, C. R. Jacob and P. Ratnasamy, *Catal. Today*, 1999, **49**, 171.
- C. Espro, F. Arena, F. Tasselli, A. Regina, E. Drioli and A. Parmeliana, *Catal. Today*, 2006, **118**, 253.
- M. G. Clerici, *Appl. Catal.*, 1991, **68**, 249.
- J. Q. Lu, X. Zhang, J. J. Bravo-Suárez, K. K. Bando, T. Fujitani and S. T. Oyama, *J. Catal.*, 2007, **250**, 350.
- S. Bordiga, F. Bonino, A. Damin and C. Lamberti, *Phys. Chem. Chem. Phys.*, 2007, **9**, 4854.
- P. Ratnasamy, D. Srinivas and H. Knözinger, *Adv. Catal.*, 2004, **48**, 1.
- T. Hayashi, K. Tanaka and M. Haruta, *J. Catal.*, 1998, **178**, 566.
- J. J. Bravo-Suárez, K. K. Bando, J. Q. Lu, M. Haruta, T. Fujitani and S. T. Oyama, *J. Phys. Chem. C*, 2008, **112**, 1115.
- U. Kreibitz and M. Vollmer, *Optical Properties of Metal Clusters*, Springer, Berlin, 1995.
- B. Chowdhury, J. J. Bravo-Suárez, N. Mimura, J. Q. Lu, K. K. Bando, S. Tsubota and M. Haruta, *J. Phys. Chem. B*, 2006, **110**, 22995.
- J. J. Bravo-Suárez, K. K. Bando, J. Q. Lu, T. Fujitani and S. T. Oyama, *J. Catal.*, 2008, **255**, 114.
- C. Reed, Y. Xi and S. T. Oyama, *J. Catal.*, 2005, **235**, 378.
- C. B. Khouw, C. B. Darrt, J. A. Labinger and M. E. Davis, *J. Catal.*, 1994, **149**, 195.
- J. Cunningham, B. K. Hodnett, M. Ilyas, J. Tobin, E. L. Leahy and J. L. G. Fierro, *Faraday Discuss. Chem. Soc.*, 1981, **72**, 283.
- V. K. Díez, C. R. Apesteguía and J. I. Di Cosimo, *Catal. Today*, 2000, **63**, 53; J. I. Di Cosimo, V. K. Díez, M. Xu, E. Iglesia and C. R. Apesteguía, *J. Catal.*, 1998, **178**, 499.
- M. A. Aramendía, V. Borau, C. Jiménez, J. M. Marinas, A. Porras and F. J. Urbano, *J. Catal.*, 1996, **161**, 829.
- J. March, in *Advanced Organic Chemistry. Reactions, Mechanisms, and Structure*, Wiley, New York, 4th edn, 1992, p. 290.
- I. Yamanaka, S. Hasegawa and K. Otsuka, *Appl. Catal., A*, 2002, **226**, 305.